

The Utilization of Sago Waste as the Raw Material in the Production of Activated Carbon Electrodes for an Electrochemical Double-Layer Capacitor 130795

By E.Taer

The Utilization of Sago Waste as the Raw Material in the Production of Activated Carbon Electrodes for an Electrochemical Double-Layer Capacitor

*E.Taer, ¹A. Afrianda, ¹Apriwandi, ²R. Taslim, ¹A. Agustino, ¹Awitdrus, and ¹R. Farma

8

¹ Department of Physics, University of Riau, 28293 Simpang Baru, Riau, Indonesia

² Departement of Industrial Engineering, Islamic State University of Sultan Syarif Kasim, 28293 Simpang Baru, Riau, Indonesia.

*E-mail: erman.taer@yahoo.com

Received: 1 xxx 2018 / Accepted: 1 xxx 2018 / Published: 1 xxx 2018

Research on the utilization of sago waste as an activated carbon electrode for an electrochemical double-layer capacitor (EDLC) has been successfully performed. An important part of the EDLC is the highly porous activated carbon electrode that is prepared without the addition of adhesive materials with an optimum physical activation time. The sago waste-based activated carbon was prepared without adhesive materials with different physical activation time of 0.5, 1.0, 1.5, 2.0 and 2.5 hours. The effect of the physical activation time is discussed in terms of the physical and electrochemical properties of the carbon electrodes. The evaluated physical properties of the electrode include density, surface morphology, chemical element content, degree of crystallinity and surface area. The electrochemical properties of the supercapacitor cells were studied for specific capacitances on a two-electrode system using the cyclic voltammetry method. The optimum specific capacitance of the sample electrode was 132 F g^{-1} , which was achieved with an activation time of 2.5 hours.

Keywords: sago waste; physical activation time; supercapacitor

1. INTRODUCTION

Sago (*Metroxylon* sp.) is an indigenous plant in Indonesia, which has an area of approximately 1.128 million hectares of sago, representing 51.3% of the world's sago. Every year, Indonesia exports 200000 to 260000 tons of sago [1]. The processing of sago produces a waste of 75-83% [2], and this waste contains 21% lignin, 20% cellulose, extractive substances and ashes [3]. Sago waste is still limited to a few simple uses such as animal feed [4], weed control [5] and plant fertilizers. The content of lignin and cellulose is high enough so that it is very possible to use sago waste as activated carbon [6]. Sago

waste is one of the categories of materials used to produce activated carbon for supercapacitor applications because it has a surface area as high as $1737 \text{ m}^2 \text{ g}^{-1}$ by a simple activation process [7]. Supercapacitor is an energy storage device that is currently being developed by researchers [8]. In previous studies, the utilization of sago waste as a carbon electrode was carried out by Aripin et al. in 2010 [9] and Afrianda et al., in 2018 [10]. Aripin's samples were prepared by two different activation methods. The first method is a chemical activation process consisting of KOH and carbon with ratios of 1: 1, 2: 1, 3: 1 and 4: 1, followed by carbonization at high temperatures (500–900 °C). The second method was a two-step physical activation process with carbonization at a low temperature of 700 °C, followed by a physical activation at a higher temperature of 800-1000 °C. The activated carbon electrode is prepared using polytetrafluoroethylene (PTFE) as an adhesive material. Aripin's study obtained a specific capacitance of 64 F g^{-1} . Afrianda's samples were prepared with a one-stage carbonization and activation process. The samples were activated using KOH as a chemical activation agent and water steam as a physical activation agent. A physical activation time of 1.5 hours was used, which was relatively low. The carbon electrode was prepared without the addition of an adhesive material. A specific capacitance of 74 F g^{-1} was obtained for the supercapacitor cell. In this study, sago waste was processed into an activated carbon electrode for supercapacitor application without adhesive materials with longer physical activation time of 0.5, 1, 1.5, 2 and 2.5 hours. The highest specific capacitance obtained in this study was 132 F g^{-1} , which was achieved with a physical activation time of 2.5 hours.

49

2. MATERIAL AND METHODS

2.1. Preparation of the carbon electrode

The activated carbon electrode was prepared from sago waste (Dregs Sago) collected in the Selat panjang area, Riau province of Indonesia. Activated carbon was prepared by previously reported methods [11]. Chemical activation was performed using a KOH activator agent at a concentration of 0.2 M. The process of carbonization and physical activation was performed in one stage [12]. The carbonization process was carried out at a temperature of 600 °C for 2 hours under a N_2 atmosphere, followed by a physical activation at a temperature of 850 °C in a water steam environment. The water steam was maintained for various activation time of 0.5, 1, 1.5, 2 and 2.5 hours. The samples are labeled DS-0.5, DS-1, DS-1.5, DS-2 and DS-2.5, respectively, where DS refers to dregs sago and the number refers to the activation time. Lastly, all samples were polished and washed until the water became neutral.

2.2. Cell fabrication and electrochemical characteristics

Supercapacitor cells were fabricated in a sandwich type consisting of activated carbon electrodes, separators, current collectors, and electrolyte [13]. In this study, the separator was an eggshell membrane that has been previously reported [14]. The current collectors were a 316 L stainless steel tape purchased from Goodfellow Cambridge Ltd., England. An aqueous electrolyte was selected as the electrolyte for supercapacitor cells, i.e., H_2SO_4 with a concentration of 1 M purchased from Germany [15].

2.3. Physical and electrochemical characteristics

The physical and electrochemical properties were characterized for the activated carbon electrodes. The studied physical properties of the carbon electrode include the density, surface morphology, chemical composition, degree of crystallinity and surface area. The densities were obtained by measuring the mass and the volume. The surface morphology was examined by scanning electron microscopy (SEM). The SEM magnifications used were 5000 and 40000 times. The chemical composition was measured using energy dispersive X-ray (EDX). Measurements of the surface morphology and the chemical composition of the samples through SEM and EDX methods were performed with a JEOL JSM-6510 LA instrument. The degree of crystallinity was measured by X-ray diffraction method (XRD) using a Philip X-Pert Pro PW 3060/10 instrument with a Cu K- α light source and a wavelength of 1.5418 Å. The surface area was analyzed using N₂ adsorption-desorption isotherms with a Quantachrome NovaWin Version 11.0 instrument. The electrochemical properties, i.e., the specific capacitance of the supercapacitor cell, were studied using cyclic voltammetry (CV) method with a Physic CV UR Rad-Er 5841 instrument, which has been calibrated with a 1280 Solartron device. The specific capacitance was evaluated by a standard formula [16-17].

3. RESULTS AND DISCUSSION

3.1. Density analysis

The density analysis was performed by measuring the mass and the volume before and after the pyrolysis. Table 1 shows the mass, volume and density before and after the pyrolysis. Based on the data shown in Table 1, the physical activation time has a very significant effect on the mass, volume and density of the carbon electrode. In general, the mass, volume and density decrease with increasing physical activation time. The sample mass decreases regularly with increasing activation time, while the volume also decreases but not as regularly. The increasing activation time results in a smaller density. The density decrease occurred in a range of 13.91-21.82%.

Table 1. The mass, volume and density before and after pyrolysis

Sample Codes	Before Pyrolysis			After Pyrolysis		
	Mass	Volume	Density	Mass	Volume	Density
DS-0.5	0.654	0.629	1.042	0.243	0.271	0.899
DS-1.0	0.663	0.641	1.037	0.241	0.272	0.889
DS-1.5	0.656	0.628	1.046	0.224	0.264	0.850
DS-2.0	0.651	0.624	1.044	0.222	0.268	0.834
DS-2.5	0.626	0.598	1.048	0.219	0.275	0.799

The largest decrease in the mass, volume and density occurred in the DS-2.5 samples. The DS-2.5 sample has a longer reaction between H₂O, an activation agent, and the carbon material in the electrode sample, which breaks more carbon chains and causes an optimal evaporation of the impurities,

thus leading to more pores and a lower density [18]. This ³⁶ is similar to the carbon electrode made from rubber wood sawdust [13]. This analysis indicates that 2.5 hours is the optimum physical activation time to produce the best electrode sample.

3.2. Analysis of the capacitive properties

The electrochemical properties were measured using cyclic voltammetry (CV) method, and the CV data is shown in Figure 1. Figure 1.a shows the charge-discharge current in a potential window of 0-0.5 V at a scan rate of 1 mV s⁻¹. The I-V data for a typical type of carbon electrode material is a rectangular shape [19]. This area indicates that the charge/discharge response for the samples is almost purely electrostatic without a pseudocapacitive phenomenon. The curve area formed represents the specific capacitance produced by the carbon electrode [20].

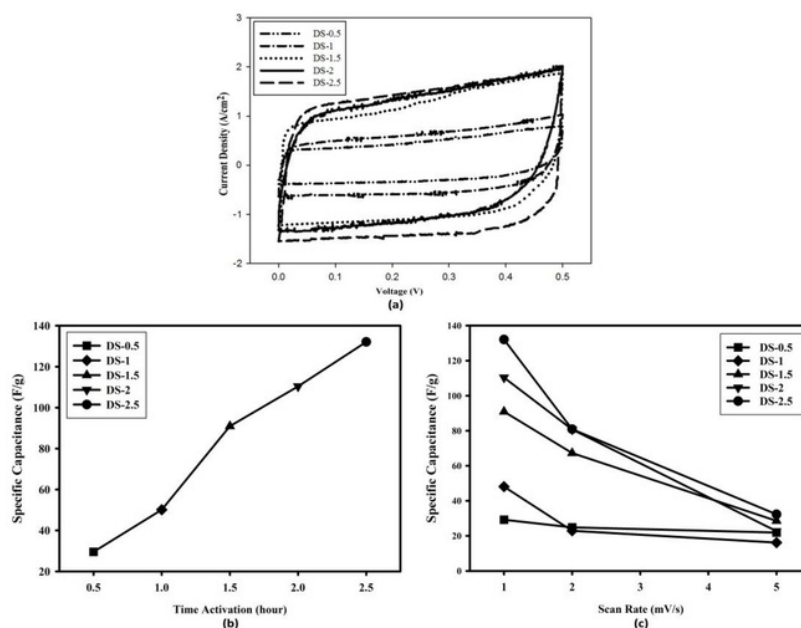


Figure 1. a) CV curves for all samples; b) the effect of the physical activation time on the capacitive properties; c) the specific capacitance (F g^{-1}) vs the scanning rate (mVs^{-1}) for different supercapacitor cells.

The charging process begins when the potential is relatively low on the CV instrument, and the electrolyte ions rapidly charge in to the pores of the electrode, so the current density increases significantly. The ion charging process continues until the maximum potential is reached. After this process is complete, the CV instrument starts the discharging process, where the electrolyte ions simultaneously discharge from the pores of the carbon electrode and the current density decreased significantly. The ion discharging continues until the initial potential is reached. A greater I-V area of the electrodes with a higher specific capacitance was produced by a longer physical activation time [21]. Specific capacitances obtained in this study were 29.21 F g^{-1} , 48.12 F g^{-1} , 90.96 F g^{-1} and 132.09 F g^{-1}

for the DS-0.5, DS-1.0, DS-1.5, DS-2.0 and DS-2.5 samples, respectively. The maximum capacitance produced was higher than that produced with the same base material in Aripin's and Afrianda's studies, which were 64 F g^{-1} and 74 F g^{-1} , respectively. Figure 1.b shows that the physical activation time affects the capacitive properties of the supercapacitor at a scan rate of 1 mV s^{-1} . Increasing the activation time causes a longer reaction between the carbon and the activation agent. This reaction causes more carbon chains to break and produces more pores. Increasing the pores of the carbon electrode increases the porosity and the surface area of the sample. As a result, the ion diffusion into the pores increases, and the specific capacitance will be higher.

The effect of the scan rate on the specific capacitance is also analyzed and shown in Figure 1.c. The scan rates used are 1 mV s^{-1} , 2 mV s^{-1} and 5 mV s^{-1} . The increasing scan rate affects the specific capacitance of all samples. A higher scan rate results in a shorter time for the electrolyte ions to seep into the pores of the carbon electrode, thus resulting in a smaller specific capacitance. Increasing the activation time causes the carbon particles to split into smaller parts, which indicates that the electrodes are produced with smaller and narrower carbon pores [22]. An activation time of 0.5 hours produces a large pore size, and the electrolyte ions easily seep into the pores of the carbon electrode, so the variation of the scanning rate has no effect. A higher activation time results in smaller pore sizes, and the ions take longer to seep into the pores of the carbon electrode. The specific capacitance decreases significantly with increasing scan rate.

3.3. Analysis of the surface morphology

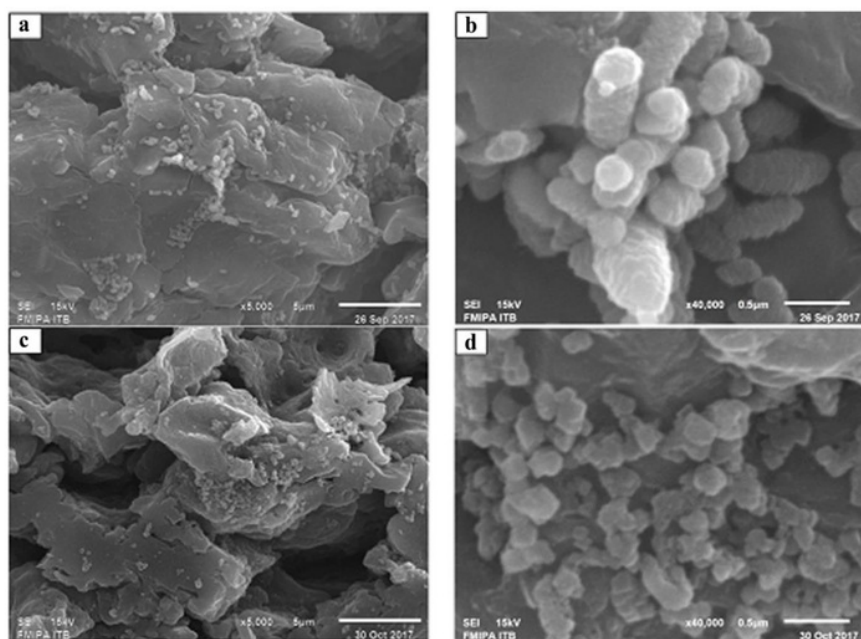


Figure 2. SEM micrographs for a) DS-1.5 with a magnification of 5000 times; b) DS-1.5 with a magnification of 40000 times; c) DS-2.5 with a magnification of 5000 times; d) DS-2.5 with a magnification of 40000 times.

SEM micrographs for the DS 1.5 and DS-2.5 samples with magnifications of 5000 and 40000 times are shown in Figure 2. The SEM micrographs show uneven macropores that exist between the particles with a pore size in the range of 1.3-5.53 μm . The pores formed appear to be an elongated and irregular shape. There are lumps of small carbon particles on the surface of the carbon electrode. The sizes of the carbon particles formed are large, in the range of 0.24-0.5 μm . The sizes of the particles and the pores formed are smaller than the particles in the previously reported sample.

The surface morphology is influenced by the activation time, and a longer activation time causes the particle and the pore sizes to decrease. Increased activation time causes a longer reaction between carbon and steam, thus breaking more carbon chains. Breaking the carbon chain results in cracks and fragments, which forms smaller particles. In addition, increased activation time also causes a faster particle movement, resulting in more particle collisions, which causes the carbon particles to split into smaller parts [22].

3.4. Analysis of the chemical composition

The chemical composition of the sample was measured using the energy dispersive X-ray (EDX) method. The results of the EDX spectra showing the chemical composition of the DS-1.5 and DS-2.5 samples are shown in Figure 3 and Table 2. Table 2 shows that the chemical composition of the sample is dominated by the carbon element (C). In addition to carbon, there are also other elements, such as oxygen (O), magnesium (Mg), potassium (K) and calcium (Ca). The presence of the oxygen element as the second highest composition is due to the carbonization process when the oxygen content in the sample electrode is not completely decomposed. Ca, which is one of the chemical contents in sago waste, has a high boiling point of 1484 $^{\circ}\text{C}$, so it does not decompose during the process of carbonization and physical activation. The Mg element probably comes from the steel balls that collide with the sample during the smoothing process. The presence of the K element comes from the chemical compound KOH, an activator agent, because the water is not perfectly neutral during the process of washing the sample. The carbon quantity in the DS-2.5 sample is 97.13%, greater than that in the DS-1.5 sample, which is only 89.99%. Increased activation time causes more contents of the elements other than carbon to decompose, so the carbon element produced was higher. The carbon content obtained in this study is also similar to the previously reported carbon content with different carbon materials, such as 98.35% from durian [18] and 87.86% from banana stem [23].

Table 2. The chemical composition of the DS-1.5 and DS-2.5 samples

unsaes	DS-1.5		DS-2.5	
	Mass %	Atom %	Massa %	Atom %
C	85.45	89.99	94.42	97.13
O	11.34	8.96	2.35	1.81
Mg	0.17	0.09	0.25	0.13
K	-	-	1.11	0.35
Ca	3.04	0.96	1.87	0.58
Totals	100%			

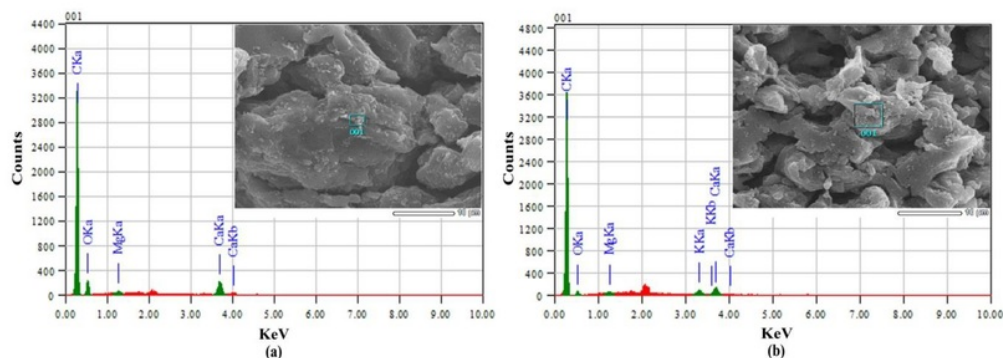


Figure 3. The EDX spectra of the DS-1.5 and DS-2.5 samples

3.5. Analysis of the X-ray diffraction, crystallite dimension and surface area

X-ray diffraction analysis (XRD) was performed to determine the nature of the crystallinity in the carbon electrode. The diffraction 2θ angles used are in the range of 10° - 100° . Figure 4 shows the XRD patterns for the DS-1.5 and DS-2.5 samples, which exhibit a broadening peak shape, indicating an amorphous structure for carbon materials from biomass materials [24]. The 2θ angles of the 002 and 100 reflection planes for the DS-1.5 sample are 24.649° and 44.420° , respectively, while the 2θ angles of the 002 and 100 reflection planes for the DS-2.5 sample are 24.746° and 44.052° , respectively. These data suggest that the samples have a good peak coverage for carbon materials [13]. The composition of the carbon structure is also indicated by a 2θ angle of 84.107° for the 112 reflection plane. Elements and compounds other than carbon are also found in the X-ray diffraction results, as evidenced by the presence of sharp and narrow peaks in the X-ray diffraction pattern. The peaks shown on the DS-1.5 sample curve are from CaCO_3 , whereas the peaks shown in the DS-2.5 sample are from CO and CaCO_3 .

Table 3. The interlayer spacing and the microcrystallite of the DS-1.5 and DS-2.5 samples

Kode Elektroda	$2\theta_{(002)}$ ($^\circ$)	$2\theta_{(100)}$ ($^\circ$)	$d_{(002)}$ (\AA)	$d_{(100)}$ (\AA)	Lc (\AA)	La (\AA)
DS-1,5	24,694	44,42	3,602364	2,037818	11,82018	24,02344
DS-2,5	24,746	44,052	3,594912	2,053984	10,79225	41,77059

Increased activation time resulted in different interlayer spacings and microcrystallite dimensions, as shown in Table 3. The interlayer spacing (d_{hkl}) is calculated using the Bragg equation, i.e., [25]

$$n\lambda = 2d \sin \theta \quad (1)$$

The microcrystallite dimensions, such as the steak height (L_c) and the steak width (L_a), are calculated using the following equations [26, 27, 28, 29]:

$$L_a = 1.94 \lambda / \beta \cos \theta_{(100)} \quad (2)$$

$$L_c = 0.89 \lambda / \beta \cos \theta_{(002)} \quad (3)$$

where L_c and L_a are the dimensions of the microcrystallites (\AA), λ is the wavelength (\AA), β is the bandwidth (degree), $\theta_{(100)}$ is the diffraction angle in the hkl plane 100 and $\theta_{(002)}$ is the diffraction angle in the hkl plane 002. Increased physical activation time generally does not have a significant effect.

The microcrystallite dimensions, L_c and L_a , in the range of 10.66–12.23 \AA are almost identical to those of the activated carbon from other biomass materials, such as durian shell, in the range of 10.58–36.21 \AA [18]. These data is still in the data range for activated carbon [13]. The stake height can be used to determine the surface area of the electrode sample using the empirical formula [30]:

$$SSA_{\text{xrd}} = 2/(\rho_{\text{xrd}}L_c) \quad (4)$$

where ρ_{xrd} is the XRD density, which is evaluated using the following equation:

$$\rho_{\text{xrd}} = (d_{002}(\text{white})/d_{002}(\text{sample})) \rho(\text{graphite}) \quad (5)$$

where $d_{002}(\text{graphite})$ and $\rho(\text{graphite})$ are 0.33354 nm and 2.268 g cm^{-3} , respectively [30]. The surface area of the sample electrode is shown in Table 3. As seen in Table 4, the microcrystalline dimensions are strongly associated with the surface area. A small microcrystallite height is required to produce a high surface area of activated carbon. DS-2.5 samples have a high surface area of 880.70 $\text{m}^2 \text{g}^{-1}$, which is almost the same as the electrode surface area of other materials, such as coffee shell and cassava peel waste, which are 842 $\text{m}^2 \text{g}^{-1}$ [31] and 1352 $\text{m}^2 \text{g}^{-1}$ [32], respectively.

Table 4. The surface area from XRD for the DS-1.5 and DS-2.5 samples

Sample code	$d_{(002)}$ (\AA)	L_c (\AA)	ρ_{xrd} ($\text{g} \cdot \text{cm}^{-3}$)	SSA_{xrd} ($\text{m}^2 \cdot \text{g}^{-1}$)
DS-1.5	3,602364	11,82018	2.0999	805.32 $\text{m}^2 \cdot \text{g}^{-1}$
DS-2.5	3,594912	10,79225	2.1042	880.70 $\text{m}^2 \cdot \text{g}^{-1}$

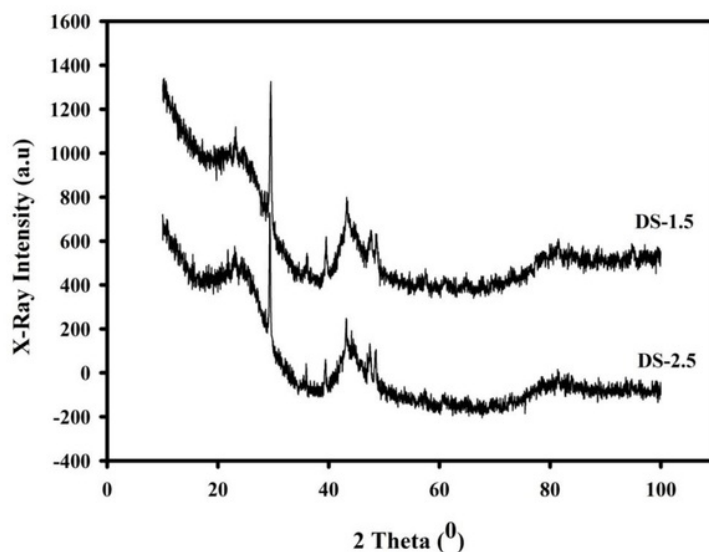


Figure 4. The XRD patterns for the DS-1.5 and DS-2.5 samples

The analysis of the physical and electrochemical properties shows interrelated data. The density and the microcrystalline height decrease with increasing physical activation time. Decreasing density and microcrystalline height result in a good porosity, so the surface area of the electrode increases; this is followed by the increase in the carbon content and the capacitive properties of the carbon electrodes. Based on this analysis, it can be concluded that the increase in the physical activation time increases the performance of the electrochemical double-layer capacitor and generates good physical and electrochemical properties.

4. CONCLUSION

Sago waste was found to be one potential candidate as an activated carbon electrode for the electrochemical double-layer capacitor. Sago waste is produced into activated carbon with various physical activation time without the addition of adhesive materials, resulting in good physical and electrochemical properties for EDLC applications. The carbon electrode shows a low density of 0.799 g cm^{-3} . The surface morphology shows the formation of small particles and macropores between particles. The carbon content increases with the increase in physical activation time, with the largest carbon as high as 97%. The degree of crystallinity shows that the electrode samples are made from amorphous carbon. The surface area of the sample was evaluated using a standard formula and the microcrystallinity height is $880 \text{ m}^2 \text{ g}^{-1}$ for the DS-2.5 sample. The analysis of the physical properties is supported by the electrochemical properties, which produce a specific capacitance as high as 132.09 F g^{-1} achieved in the sample with a physical activation time of 2.5 hours.

ACKNOWLEDGMENTS

The author would like to thank the DRPM Kemenristek-Dikti through the second year Project of PDUPT with the title "Potential of Urban Solid Waste Utilization as a Supercapacitor Electrode" and the contract number: 360/UN.19.5.1.3/PP/2018. The author also thanks the SEM FMIPA ITB Laboratory, which has assisted in obtaining the SEM and EDX data.

References

1. Directorate General of Estate Crops, Secretariate of Directorate General of Estate Crops, Jakarta (2016).
2. Mc. C. Will, M. I. Harley, E. R. Craig, Metroxylon Sp. Ecology papers Inc. London, (2006).
3. K. J. Kiat, Carboxymethyl Sago Waste and It's Hydrogel [thesis], University Putra Malaysia, Malaysia (2006).
4. K. Simanihuruk, A. Chaniago, J. Sirait, *Seminar Nasional Teknologi Peternakan dan Veteriner*, (2011) 542.
5. M. Syakir, M. H. Bintoro, H. Agusta, Hermanto, *Jurnal Littri* (2008) 107.
6. Nurdin, *Laporan Penelitian FKIP. Universitas Hahuoleo, Kendari*, (1995).
7. I. K. Erabee, A. Ahsan, A. W. Zularisam, S Idrus, N. N. N. Daud, T. Arunkumar, R. J. Jayamurthy, A. E. Al-Rawajfeh, *engineering journal*, 21 (2017) 1.
8. A. González, E. Goikolea, J. A. Barrena, R. Mysyk, *Renewable and Sustainable Energy Reviews*, 58 (2016) 1189.

22. H. Aripin, L. Lestari, D. Ismail, S. Sabchevski, *The Open Materials Science Journal*, 4 (2010) 117.
9. A. Afrianda, E. Taer, R. Taslim, *Jurnal Komunikasi Fisika Indonesia*, (2018) 1119.
11. 4. Taer, R. Taslim, *AIP Conf. Proc.*, 1927 (2018) 020004-1.
12. E. Taer, Apriwandi, Yusriwandi, W. S. Mustika, Zulkifli, R. Taslim, Sugianto, B. Kurniasih, Agustino, P. Dewi, *AIP Conf. Proc.*, 1927 (2018) 030036-1.
13. E. Taer, M. Deraman, I. A. Talib, A. Awitdrus, S. A. Hashmi, *Int. J. Electrochem. Si.*, 6 (2011) 1811.
14. E. Taer, Sugianto, M. A. Sumantre, R. Taslim, Iwantono, D. Dahlan, M. Deraman, *Advanced Materials Research*, 896 (2014) 66.
15. Iwantono, E. Taer, 5. A. Umar, *AIP Conf. Proc.*, 1454 (2012) 251.
16. S. Faraji, F. N. Ani, *Renew. Sust. Energ. Rev.*, 42 (2015) 823.
17. L. Q. Mai, A. Minhas-Khan, X. C. Tian, K. M. Hercule, Y. L. Zhao, X. Lin, X. Xu, *Nat. Commun.*, 4 (2013).
18. E. Taer, P. Dewi, Sugianto, R. Syech, R. Taslim, Salomo, Y. Susanti, A. Purnama, Apriwandi, Agustino, R. N. Setiadi, *AIP Conf. Proc.*, 1927 (2018) 030026-1.
17. Lee, S. Yi, S. J. Park, *Journal of Solid State Chemistry*, (2013) 158.
20. 9. J. Ra, E. Raymundo-Piñero, Y. H. Lee, F. Béguin, *Carbon*, 47 (2009) 84.
21. R. Farma, M. Deraman, A. Awitdrus, I. A. Talib, E. Taer, J. G. Manjunatha, M. M. shak, B. N. M. Dollah, S. A. Hashmi, N. H. Basri, *Bioresource Technology*, 132 (2013) 254.
22. 4. Taspika, Astuti, *Jurnal Fisika Unand*, 4(2015) 174.
23. E. Taer, Y. Susanti, Awitdrus, Sugianto, R. Taslim, R. N. Setiadi, S. Bahri, Agustino, P. Dewi, 5. Kurniasih, *AIP Conf. Proc.*, 1927 (2018) 030016-1.
24. G. Yu, L. Lei, J. Yuming, W. Yu, Y. Chuanjun, W. Yingjin, C. Gang, G. Junjie, L. Haiyan, 13. *Applied Energy*, 153 (2015) 41.
25. 12. Li, W. Chi, Z. Shen, Y. Wu, Y. Liu, H. Liu, *Fuel Process Technol.*, 91 (2010) 17.
26. P. 43. M. Carrott, J. M. V. Nabais, M. M. L. R. Carrott, J. A. Pajares, *Carbon*, 39 (2001) 1543.
27. 1. D. Cullity, *Elements of X-Ray Diffraction*, Ed. 3, (2001) Amazon Prentice Hall.
28. Awitdrus, M. Deraman, I. A. Talib, R. Omar, M.H. Jumali, E. Taer, M. H. Saman, *Sains Malaysiana*, 39 (2010) 83.
29. 1. M. V. Nabais, J. G. Teixeira, I. Almeida, *Bioresource Technology*, 102 (2010) 2781.
30. M. Deraman, R. Daik, S. Soltaninejad, N. S. M. Nor, Awitdrus, R. Farma, N. F. Mamat, N. H. 3. asri, M. A. R. Othman, *Advanced Materials Research*, 1108 (2015) 1.
31. M. R. Jisha, Y. J. Hwang, J. S. Shin, K. S. Nahm, T. P. Kumar, K. Karthikeyan, N. Dhanikaivelu, D. Kalpana, N. G. Renganathan, A. M. Stephan, *Material Chemistry and Physics*, 115 (2009) 33–39.
32. A. E. Ismanto, S. Wang, F. E. Soetaredjo, S. Ismadji, *Bioresource Technology*, 101 (2010) 3534.

The Utilization of Sago Waste as the Raw Material in the Production of Activated Carbon Electrodes for an Electrochemical Double-Layer Capacitor 130795

ORIGINALITY REPORT

25%

SIMILARITY INDEX

PRIMARY SOURCES

- | | | |
|---|---|----------------|
| 1 | electrochemsci.org
Internet | 117 words — 3% |
| 2 | E. Taer, P. Dewi, Sugianto, R. Syech, R. Taslim, Salomo, Y. Susanti, A. Purnama, Apriwandi, Agustino, R. N. Setiadi. "The synthesis of carbon electrode supercapacitor from durian shell based on variations in the activation time", AIP Publishing, 2018
Crossref | 112 words — 3% |
| 3 | www.electrochemsci.org
Internet | 89 words — 2% |
| 4 | aip.scitation.org
Internet | 59 words — 1% |
| 5 | Guoxiong Zhang, Yuemei Chen, Yigang Chen, Haibo Guo. "Activated biomass carbon made from bamboo as electrode material for supercapacitors", Materials Research Bulletin, 2018
Crossref | 46 words — 1% |
| 6 | Elidrissi Abderahmane. "Synthesis and characterization of the new cellulose derivative films based on the hydroxyethyl cellulose prepared from "Stipa Tenacissima" cellulose of Eastern Morocco. I. Solubility study", Journal of Applied Polymer Science, 12/05/2011
Crossref | 40 words — 1% |
| 7 | E. Taer, Y. Susanti, Awitdrus, Sugianto, R. Taslim, R. N. Setiadi, | |

S. Bahri, Agustino, P. Dewi, B. Kurniasih. "The effect of CO₂ activation temperature on the physical and electrochemical properties of activated carbon monolith from banana stem waste", AIP Publishing, 2018
36 words — 1%

Crossref

8 Erman Taer, Rika Taslim. "Brief review: Preparation techniques of biomass based activated carbon monolith electrode for supercapacitor applications", AIP Publishing, 2018
33 words — 1%

Crossref

9 Taer, Erman, Sugianto, M.A. Sumantre, Rika Taslim, Iwantono, D. Dahlan, and M. Deraman. "Eggs Shell Membrane as Natural Separator for Supercapacitor Applications", Advanced Materials Research, 2014.
26 words — 1%

Crossref

10 Erman Taer, Mohamad Deraman, Ibrahim Abu Talib, Akrajas Ali Umar, Munetaka Oyama, Rozan Mohamad Yunus. "Physical, electrochemical and supercapacitive properties of activated carbon pellets from pre-carbonized rubber wood sawdust by CO₂ activation", Current Applied Physics, 2010
26 words — 1%

Crossref

11 Wei Jiang, Fang Hu, Shunyu Yao, Zhipeng Sun, Xiang Wu. "Hierarchical NiCo₂O₄ nanowalls composed of ultrathin nanosheets as electrode materials for supercapacitor and Li ion battery applications", Materials Research Bulletin, 2017
24 words — 1%

Crossref

12 dspace.uevora.pt
20 words — < 1%

Internet

13 Hongyan Xia, Ke Wang, Shaohui Yang, Zhongqi Shi, Hongjie Wang, Jiping Wang. "Formation of graphene flowers during high temperature activation of mesocarbon microbeads with KOH", Microporous and Mesoporous Materials, 2016
18 words — < 1%

Crossref

-
- 14 M. F. Y. M. Hanappi, M. Deraman, M. Suleman, M. A. R. Othman et al. "Preparation and characterization of graphene/turbostratic carbon derived from chitosan film for supercapacitor electrodes", AIP Publishing, 2018 18 words — < 1%
Crossref
-
- 15 E. Taer, B. Kurniasih, F. P. Sari, Zulkifli, R. Taslim, Sugianto, A. Purnama, Apriwandi, Y. Susanti. "Particle size analysis on density, surface morphology and specific capacitance of carbon electrode from rubber wood sawdust", AIP Publishing, 2018 17 words — < 1%
Crossref
-
- 16 Ismat H. Ali. "Effect of Acid Extract of Leaves of Juniperus procera on Corrosion Inhibition of Carbon Steel in HCl Solutions", International Journal of Electrochemical Science, 2018 16 words — < 1%
Crossref
-
- 17 Samuel, B.A.. "Effect of pyrolysis temperature on the microstructure of disordered carbon nanowires", Thin Solid Films, 20101029 16 words — < 1%
Crossref
-
- 18 fisika.fmipa.unand.ac.id 16 words — < 1%
Internet
-
- 19 E. Taer, M. Deraman, I.A. Talib, S.A. Hashmi, A.A. Umar. "Growth of platinum nanoparticles on stainless steel 316L current collectors to improve carbon-based supercapacitor performance", Electrochimica Acta, 2011 16 words — < 1%
Crossref
-
- 20 Pertiwi Andarani, Winardi Dwi Nugraha, Wieddya. "Energy balances and greenhouse gas emissions of crude palm oil production system in Indonesia (Case study: Mill P, PT X, Sumatera Island)", AIP Publishing, 2017 15 words — < 1%
Crossref
-
- 21 diva-portal.org 15 words — < 1%
Internet

22 Aripin, Haji, Seitaro Mitsudo, Endangsusilowati S. Prima, Inyoman Nyoman Sudiana, Hikamitsu Kikuchi, Saboru Sano, and Sliven Sabchevski. "Structural Characterization of Mullite-Based Ceramic Material from Al₂O₃ and Silica Xerogel Converted from Sago Waste Ash", Advanced Materials Research, 2013.

Crossref

14 words — < 1%

23 Najah Syahirah Mohd Nor, Mohamad Deraman, Ramli Omar, Awitdrus et al. "Influence of gamma irradiation exposure on the performance of supercapacitor electrodes made from oil palm empty fruit bunches", Energy, 2015

Crossref

14 words — < 1%

24 rd.springer.com

Internet

13 words — < 1%

25 Zhong, Cheng, Yida Deng, Wenbin Hu, Jinli Qiao, Lei Zhang, and Jiujun Zhang. "A review of electrolyte materials and compositions for electrochemical supercapacitors", Chemical Society Reviews, 2015.

Crossref

11 words — < 1%

26 Natarajan Raman, Rajkumar Mahalakshmi, Muthusamy Packiaraj. "Synthesis and characterization of efficient chemical nucleases: A joint refinement from XRD, antimicrobial screening, DNA binding and cleavage investigations", Inorganic Chemistry Communications, 2014

Crossref

10 words — < 1%

27 aspdin.wifa.uni-leipzig.de

Internet

10 words — < 1%

28 Ji Yu. "Porous Core-Shell SnO₂ fibers/rGO Composite and Its Lithium Storage Performance", International Journal of Electrochemical Science, 2018

Crossref

10 words — < 1%

29 Nahil, M.A.. "Activated carbons from acrylic textile waste", Journal of Analytical and Applied Pyrolysis,

10 words — < 1%

30 Reddy, R.N.. "Porous structured vanadium oxide electrode material for electrochemical capacitors", *Journal of Power Sources*, 20060601

Crossref

10 words — < 1%

31 open.library.ubc.ca

Internet

10 words — < 1%

32 Tanayt Sinprachim, Santi Phumying, Santi Maensiri. "Electrochemical energy storage performance of electrospun AgO x -MnO x /CNF composites", *Journal of Alloys and Compounds*, 2016

Crossref

9 words — < 1%

33 Nabais, J.M.V.. "Production of activated carbons from almond shell", *Fuel Processing Technology*, 201102

Crossref

9 words — < 1%

34 www.urban-forestry.com

Internet

9 words — < 1%

35 Sanket Bhoyate, Charith K. Ranaweera, Chunyang Zhang, Tucker Morey et al. "Eco-Friendly and High Performance Supercapacitors for Elevated Temperature Applications Using Recycled Tea Leaves", *Global Challenges*, 2017

Crossref

9 words — < 1%

36 www.neliti.com

Internet

9 words — < 1%

37 Abdul Hadi, Iskandar Idris Yaacob. "Novel synthesis of nanocrystalline CeO₂ by mechanochemical and water-in-oil microemulsion methods", *Materials Letters*, 2007

Crossref

9 words — < 1%

38 D. Dahlan, N. Sartika, Astuti, E.L. Namigo, E. Taer. "Effect of TiO₂ on Duck Eggshell

9 words — < 1%

- 39 Wen Zhou. "Effect of a High Concentration of Chloride Ions on the Corrosion Behaviour of X80 Pipeline Steel in 0.5 mol L⁻¹ NaHCO₃ Solutions", International Journal of Electrochemical Science, 2018 8 words — < 1%

Crossref

- 40 Suxian Liu. "Controlled Synthesis of Co₃O₄ Electrocatalysts with Different Morphologies and Their Application for Oxygen Evolution Reaction", International Journal of Electrochemical Science, 2018 8 words — < 1%

Crossref

- 41 Karuppiyah Pandi. "Hydrothermal Synthesis of Carbon Coated NiCo₂O₄ Nano flower for the Electrochemical Oxidation of Sulfite in Real Sample", International Journal of Electrochemical Science, 2018 8 words — < 1%

Crossref

- 42 Daolin Zhu. "NiO/ZnO Nanocomposite as Electrode Material for Supercapacitors", International Journal of Electrochemical Science, 2018 8 words — < 1%

Crossref

- 43 www.diva-portal.org 8 words — < 1%

Internet

- 44 citeseerx.ist.psu.edu 8 words — < 1%

Internet

- 45 Ji-Dong Gu. "Degradation and mineralization of cellulose acetate in simulated thermophilic compost environments", Journal of Environmental Polymer Degradation, 10/1993 8 words — < 1%

Crossref

- 46 Samios, E.. "Preparation, characterization and biodegradation studies on cellulose acetates with varying degrees of substitution", Polymer, 199706 8 words — < 1%

Crossref

47 Yu Li, Bing Guan, Aimee MacLennan, Yongfeng Hu, Dandan Li, Jing Zhao, Yaqiong Wang, Huaihao Zhang. "Porous waxberry-like MnO₂/La₂O₃ microspheres for high performance asymmetric supercapacitor", *Electrochimica Acta*, 2017

8 words — < 1%

Crossref

48 pubs.rsc.org
Internet

8 words — < 1%

49 Zehong Chen, Xinwen Peng, Xiaoting Zhang, Shuangshuang Jing, Linxin Zhong, Runcang Sun. "Facile synthesis of cellulose-based carbon with tunable N content for potential supercapacitor application", *Carbohydrate Polymers*, 2017

8 words — < 1%

Crossref

50 Peng, Xu, Lele Peng, Changzheng Wu, and Yi Xie. "Two dimensional nanomaterials for flexible supercapacitors", *Chemical Society Reviews*, 2014.

8 words — < 1%

Crossref

51 N.H. Basri, M. Deraman, S. Kanwal, I.A. Talib, J.G. Manjunatha, A.A. Aziz, R. Farma. "Supercapacitors using binderless composite monolith electrodes from carbon nanotubes and pre-carbonized biomass residues", *Biomass and Bioenergy*, 2013

8 words — < 1%

Crossref

52 Mohamad Redwani Mohd Jasni, Mohamad Deraman, Ellisa Hamdan, Noor Ezniera Shafieza Sazali et al. "Effect of KOH Treated Graphene in Green Monoliths of Pre-Carbonized Biomass Fibers on the Structure, Porosity and Capacitance of Supercapacitors Carbon Electrodes", *Materials Science Forum*, 2016

8 words — < 1%

Crossref

53 Basri, N.H., M. Deraman, S. Kanwal, I.A. Talib, J.G. Manjunatha, A.A. Aziz, and R. Farma. "Supercapacitors using binderless composite monolith electrodes from carbon nanotubes and pre-carbonized biomass residues",

8 words — < 1%

54 Jiang, Junhua, Lei Zhang, Xinying Wang, Nancy Holm, Kishore Rajagopalan, Fanglin Chen, and Shuguo Ma. "Highly ordered macroporous woody biochar with ultra-high carbon content as supercapacitor electrodes", *Electrochimica Acta*, 2013. 8 words — < 1%

Crossref

55 Cristina E Savencu. "Corrosion Behaviour of Co-Cr Dental Alloys Processed by Alternative CAD/CAM Technologies in Artificial Saliva Solutions", *International Journal of Electrochemical Science*, 2018 7 words — < 1%

Crossref

56 Chellaian Justin Dhanaraj, Madhavan Sivasankaran Nair. "Synthesis and characterization of metal(II) complexes of poly(3-nitrobenzylidene-1-naphthylamine-co-succinic anhydride)", *European Polymer Journal*, 2009 7 words — < 1%

Crossref

57 Suleman, Mohd., M.A.R. Othman, S.A. Hashmi, Yogesh Kumar, Mohamad Deraman, R. Omar, and M.R.M. Jasni. "Activated graphene oxide/reduced graphene oxide electrodes and low viscous sulfonium cation based ionic liquid incorporated flexible gel polymer electrolyte for high rate supercapacitors", *Journal of Alloys and Compounds*, 2016. 7 words — < 1%

Crossref

58 Chuanli Qin, Xing Lu, Geping Yin, Zheng Jin, Qiang Tan, Xuduo Bai. "Study of activated nitrogen-enriched carbon and nitrogen-enriched carbon/carbon aerogel composite as cathode materials for supercapacitors", *Materials Chemistry and Physics*, 2011 6 words — < 1%

Crossref

59 Careem, M.A.. "A voltammetry study on the diffusion of counter ions in polypyrrole films", *Journal of Power Sources*, 20060913 6 words — < 1%

Crossref

EXCLUDE QUOTES OFF
EXCLUDE BIBLIOGRAPHY OFF

EXCLUDE MATCHES OFF